

Prior to following the instructions below, verify that this document is the latest version in use. The latest version can be found at www.barsplice.com.

4900 Webster Street • Dayton, OH 45414 • Ph: (937) 275-8700


INSTALLATION INSTRUCTIONS FOR FIELD ASSEMBLY OF BPI® BARSPLICER STRUCTURAL CONNECTOR

FABRICATOR IS RESPONSIBLE FOR PROVIDING THESE INSTRUCTIONS TO THE PLACER AND/OR CONTRACTOR.

Internal Structural Connector threads are protected by plastic plugs and rebar threads are protected by plastic caps, both of which should be kept in place until time of welding and assembly. If missing, obtain the correct caps and/or plugs from the manufacturer. If thread damage is discovered, it must be corrected before assembly to avoid premature binding. Minor thread damage can be fixed using a thread file, or a thread cleaning tool. DO NOT TRY TO ASSEMBLE DAMAGED THREADS. All Structural Connectors are marked with the intended rebar size. DO NOT USE WITH REBAR THAT IS LARGER OR SMALLER THAN THE INTENDED BAR SIZE, OR WITH REBAR THREADS OTHER THAN UNIFIED NATIONAL COURSE (UNC). STORE BARSPLICER STUCTURAL CONNECTORS AND BPI® THREADED BAR IN A CLEAN, DRY PLACE UNTIL READY TO INSTALL.

- CAUTION: Remove plastic PLUG in Structural Connector prior to welding. If installing in stages, be sure to reinstall the plug in the Structural Connector after welding (when connector has cooled to ambient temperature) to protect the threads until it is time to assemble with threaded bar. Weld surfaces should be cleaned as needed.
- Using electrode E7018 (or equivalent for low carbon steel, Grade 1018) fillet weld entire circumference of the Structural Connector using weld bevel size "W" as shown in FIGURE 1. Welding to conform to AWS D1.1, Structural Welding Code. DO NOT WELD CONNECTOR IN PLACE IF THE THREADS ARE DAMAGED AND CANNOT BE REPAIRED.

FIGURE 1: WELDING STRUCTURAL CONNECTOR

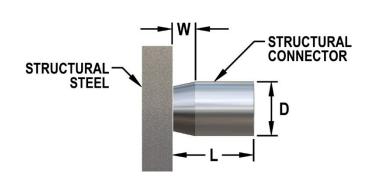


| REBAR SIZE | STR. CONN. LENGTH | STR. CONN. DIAMETER | WELD BEVEL SIZE |
|-------------------|-------------------------------|--------------------------------------|------------------------------|
| US (metric) [CAN] | `` L ″ (in) | `` D ″ (in) | ` `W ″ (in) |
| #4 (13) [10M] | 1 ³ /8 | ⁷ /8 | ³ / ₁₆ |
| #5 (16) [15M] | 1 ¹ / ₂ | 1 | 1/4 |
| #6 (19) [20M] | 1 ³ /4 | 1 ¹ / ₄ | 1/4 |
| #7 (22) | 2 | 1 ³ / ₈ | ⁵ / ₁₆ |
| #8 (25) [25M] | 2 ¹ / ₄ | 1 ⁵ /8 | ³ /8 |
| #9 (28) [30M] | 2 ⁵ /8 | 1 ³ /4 | ⁷ / ₁₆ |
| #10 (32) | 3 | 2 | 1/2 |
| #11 (36) [35M] | 3 ³ /8 | 2 | ⁹ / ₁₆ |

- 2) Remove the protective cap from the threaded bar and check both external (rebar) and internal (Structural Connector) threads for cleanliness. Clean off any debris and/or foreign matter. DO NOT USE CORROSIVE ACIDS. Any thread damage must be corrected as noted above prior to installation.
- 3) Locate the threaded bar and Structural Connector, and line them up as straight as possible. See **FIGURE 2** for preassembled connection. Align the COUPLER and CONNECTOR so that the threads will screw together without binding.

FIGURE 2: PREASSEMBLED CONNECTION

Please direct all assembly questions to BarSplice Products, Inc. Page 1 of 2 4) After the initial thread location, rotate the free rebar clockwise making sure the threaded bar and Structural Connector remain aligned. If you feel the threads starting to prematurely bind, DO NOT FORCE THEM. Shake the free end of the rebar while turning, allowing the free end of the rebar to rotate in its own natural circle with the Structural Connector threads aligned. Continue to rotate until FULLY ENGAGED and SNUG. See FIGURE 3 for assembled connection.

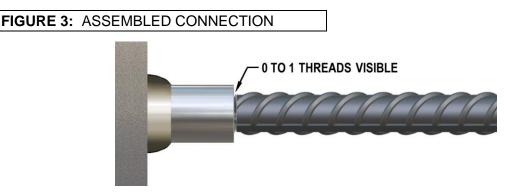

- NOTE: If the threaded rebar and coupler threads do not properly engage during assembly, stop immediately. Disassemble the connection to determine the problem. Possible causes of mis-assembly may be mis-matched thread sizes, contaminated threads (i.e. concrete, dirt, etc.) or damaged threads. Re-assemble only after the problem has been identified and corrected.
- 5) A chain wrench or pipe wrench can be used to snug and tighten the threaded bar and Structural Connector as needed. Always consider your own **personal safety**. Make sure you are securely positioned and that you will not slip or fall during installation.
 - NOTE: Long lengths of rebar, especially large diameter bars, are heavy. To overcome rebar weight, it may be necessary to use an extension bar. As necessary, use the following wrench lengths as a guide: Bar sizes #3 #6 (10-19 mm) = 8 12" (20-30 cm) length; Sizes #7 #8 (22-25 mm) = 12 18" (30-45 cm) length; and Sizes #9 #11 (29 36 mm) = 18 24" (45-60 cm) length. DO NOT WIRE TIE BARS UNTIL AFTER FULL ASSEMBLY.
- 6) After assembly, inspect for proper thread engagement. For Barsplicer threads, some variation in the number of exposed threads is natural due to the thread tolerance and run-out. In general, it is typical to see 0 to 1 complete thread(s) after full assembly, per FIGURE 3. If needed, fully assembled threads can be double-checked by the application of a chain wrench or pipe wrench as described above, to ensure the couplers are snug. IT IS NOT NECESSARY TO USE A TORQUE WRENCH OR APPLY A HIGH TORQUE VALUE.